

C-axis Penetration Depth and Inter-layer Conductivity in the Thallium Based Cuprate Superconductors

Diana Dulić, D. van der Marel, A. A. Tsvetkov*

Laboratory of Solid State Physics, Materials Science Centre, Nijenborgh 4, 9747 AG Groningen, The Netherlands

W. N. Hardy

Department of Physics and Astronomy, University of British Columbia, Vancouver, BC, V6T 1Z1, Canada

Z. F. Ren and J. H. Wang

Department of Chemistry, SUNY at Buffalo, Buffalo NY 14260-3000, USA

B. A. Willemsen

Superconductor Technologies Inc., Santa Barbara, CA 93111-2310

(February 1, 2008)

The c -axis Josephson plasmons in optimally doped single-layer and bi-layer high T_c cuprates $\text{Th}_2\text{Ba}_2\text{CuO}_6$ and $\text{Th}_2\text{Ba}_2\text{CaCu}_2\text{O}_8$ have been investigated using infrared spectroscopy. We observed the plasma frequencies for these two compounds at 27.8 and 25.6 cm^{-1} respectively, which we interpret as a Josephson resonances across the TlO blocking layers. No maximum in the temperature dependence of the c -axis conductivity was observed below T_c , indicating that even in the superconducting state a coherent quasi-particle contribution to the c -axis conductivity is absent or very weak, in contrast to the behaviour of the ab -plane conductivity.

74.72.-h, 74.25.Gz

Studies of the c -axis properties in High- T_c superconductors are of considerable importance. Although the materials are highly anisotropic, with much of the physics being of a two dimensional nature, it is clear that an understanding of both the c -axis and ab -plane behavior is relevant to the quest for the mechanism of high- T_c superconductivity. It is already well established that the normal state c -axis transport in these materials is strongly incoherent. A number of theories treat this problem, and generally they can be divided into two categories, *i.e.* Fermi-liquid and non-Fermi-liquid approaches. The Fermi-liquid approaches rely on special properties of the quasi-particle scattering, *e.g.* a strong momentum dependence along the quasi two-dimensional Fermi surface of the quasiparticles [1]. Within the non-Fermi-liquid approaches the transport processes involve particles carrying unconventional spin and charge quantum numbers. One of the most radical approaches, based on spin-charge separation in the copper oxide planes, has resulted in the notion of 'confinement' of single charge carriers to the copper-oxide planes in the normal state [2]. Within the latter class of models the formation of Cooper-pairs is accompanied by deconfinement of those pairs, resulting in a center-of-mass kinetic energy gain. In principle this also provides a mechanism for superconductivity [3], and a fundamental experimental test of this hypothesis was proposed by Anderson [4]. The experimental results indicated that interlayer tunneling of pairs is *not* the main mechanism for superconductivity, at least in $\text{Th}_2\text{Ba}_2\text{CuO}_6$ [5–7]. This immediately raises the question of whether the incoherent c -axis transport arises from 2-dimensional confinement of single charge carriers to the copper oxide planes, and whether or not confinement persists in the superconducting state.

From an analysis of the infrared reflectivity spectra using the 2-fluid model, Tamasaku *et al.* [8] have concluded that for $T < T_c$ the c -axis quasi-particle scattering rate of $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ for $T < T_c$ decreases strongly with temperature, and "the T dependence looks very similar to that for the quasiparticle scattering rate in the ab plane". This result indicated that coherent quasi-particle transport is recovered simultaneously with the occurrence of a finite critical current along the c -direction. A different result was later obtained by J.H. Kim *et al.* [9]. Experimentally the c -axis transport was monitored via the temperature dependence of the real part of the conductivity, $\sigma_c(\omega)$, which exhibited a sharp drop below T_c . The drop in $\sigma_c(\omega)$ was attributed "exclusively to the opening of a gap, *i.e.*, without a change of the electronic scattering rate" of the carriers along the c -direction [9]. Later, similar behaviour of $\sigma_c(\omega)$ versus temperature has been reported for $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ [10], and $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ [11]. For YBCO, which at optimal doping is the least anisotropic in the normal state, the rise in σ_{ab} combined with the drop in σ_c leads to a conductivity anisotropy as large as 10^4 at low temperatures.

In this paper we address the issue of 'confinement' experimentally. We study the degree of coherence of c -axis quasi-particle transport in the superconducting state, the temperature dependence of the c -axis plasma frequency, and the role of intra-bilayer splitting by comparing the single-layer and bi-layer materials within the same family of Tl-based cuprates.

Here we report new data on epitaxially grown $\text{Ti}_2\text{Ba}_2\text{CuO}_6$ and $\text{Ti}_2\text{Ba}_2\text{CaCu}_2\text{O}_8$ thin films, with superconducting transition temperatures of 80 and 98K respectively, established by susceptibility measurements. Details of the sample preparation and growth methods have been reported elsewhere [14–16]. Dimensions of the films in the ab plane are typically 50-100 mm^2 . We measured grazing incidence reflectivity in the far infrared FIR region (17-700) cm^{-1} using a Fourier transform spectrometer. A grazing angle of 80° was chosen in order to predominantly probe the c -axis response for p -polarization of the light. Absolute reflectivities were obtained by calibrating the reflectivities against the reflectivity of a gold film deposited *in situ* on the sample without moving or rotating the sample holder.

In Fig. 1 we display the grazing incidence reflectivity of Tl2201 (Fig. 1b) and Tl2212 (Fig. 1a) in the frequency region from 17-50 cm^{-1} for various temperatures below T_c . The spectra above 50 cm^{-1} are dominated by the c -axis phonons, and a detailed analysis is presented elsewhere [17]. The only absorption below 50 cm^{-1} corresponds to the Josephson plasmon, a collective oscillation of the Cooper-pairs along the c -axis. The observed resonant frequencies (ω_J) at 4K are 27.8 cm^{-1} in Tl2201 and 25.6 cm^{-1} in Tl2212, and they redshift as the temperature approaches T_c from below. In Fig. 2 we present p -polarized reflectivity for various temperatures below T_c , normalized to the 110K spectrum (which is essentially featureless). A magnetic field of 0.35T was sufficient to shift the resonance out of our spectral window. The strong redshift upon applying an external magnetic field confirms that the absorption corresponds to the Josephson plasmon. Let us first address the question of why ω_J is almost the same in Tl2201 and Tl2212: in a model of superconducting planes weakly coupled by Josephson coupling, a separate resonance frequency is associated with each link [18]. As the only structural difference between the two materials is the insertion of an extra CuO_2 layer and a layer of Ba^{2+} ions separating the two CuO_2 layers, the same resonance frequency should appear for the link across the thallium oxide blocking layer.

We analyze the spectra using the Fresnel formula for uniaxial crystals [5]. The resonance is due to the zero-crossing of $\varepsilon_c(\omega)$, for which we adopt the standard two-fluid expression appropriate for the superconducting state

$$\varepsilon_c(\omega) = \varepsilon_S(\omega) - \frac{c^2}{\lambda_c(T)^2 \omega^2} + \frac{4\pi i \sigma_{qp}(\omega)}{\omega} \quad (1)$$

where λ_c is the c -axis penetration depth. Assuming the Josephson model to be applicable to this case, the pole-strength of the second (London) term, coming from the condensate, provides directly the critical current in the c -direction. Hence $1/\lambda_c(T)^2$ represents the superfluid density appropriate for the c -direction. Oscillations of the condensate are electromagnetically coupled to interband transitions and lattice vibrations, which are represented by the dielectric function ε_S . The third term arises from currents due to thermally activated quasi-particles. The condition for propagation of longitudinal modes in the medium along the c -direction in the long wavelength limit, is that $\varepsilon_c(\omega) = 0$, which occurs at the Josephson plasma frequency $\omega_J = c/\{\lambda_c \sqrt{\text{Re}\varepsilon_S(\omega_J)}\}$. This is also the frequency of long-wavelength plasma-polaritons propagating along the planes, which one observes in optical experiments.

The c -axis optical conductivity at the screened plasma frequency $\sigma_{qp}(\omega_J)$ determines the width of the plasma resonance in our spectra [5]. This follows from the fact that the resonance lineshape is given by

$$R_p(\omega) \approx 1 - \text{Im}e^{i\phi} \sqrt{1 - \frac{\sin^2 \theta / \text{Re}\varepsilon_S}{\omega(\omega + i\Gamma) - \omega_J(T)^2}} \quad (2)$$

where θ is the angle of incidence, and $\phi = (\pi - \text{Arg}\varepsilon_{ab})/2$ is a weakly frequency dependent phase-factor, ranging from $\phi = 0$ (ideal superconducting response) to $\phi = \pi/4$ (metallic response), and $\Gamma = 4\pi \text{Re}\sigma_{qp}(\omega_J)/\text{Re}\varepsilon_S(\omega_J)$ determines the resonance linewidth. In this expression the imaginary part of σ_{qp} has to be included in $\text{Re}\varepsilon_S$, and vice versa. We see now that the line-width of the c -axis plasma resonance is directly proportional to $\text{Re}\sigma_{qp}$ at the resonance position. This does *not* imply a direct proportionality of the plasma resonance line-width to the quasi-particle scattering rate. In fact assuming here a Drude line-shape of the quasi-particle term, $\text{Re}\sigma_{qp} = ne^2 m_{\perp}^{-1} \tau / (1 + \omega^2 \tau^2)$, the plasma resonance line-width is proportional to n_{qp}/τ if $\omega_J \tau \gg 1$ and to $n_{qp} \tau$ if $\omega_J \tau \ll 1$. In LSCO [8,9], YBCO [19], and recently Tl2201 [20] where crystals were available suitable for reflection spectroscopy on the ac -crystal face, it can be seen directly from the conductivity spectra that $\sigma_c(\omega)$ is essentially independent of frequency in the superconducting state for frequencies below $\simeq 100 \text{ cm}^{-1}$. This corresponds to the limit where $\text{Re}\sigma_{qp} \propto n_{qp} \tau$. Hence the drop of the plasma-resonance linewidth below the phase transition represents the reduction of quasi-particle density at the Fermi energy due to the opening of the superconducting gap [8].

By fitting Eq.1 to the measured spectra, using the full Fresnel expression for the grazing reflectivity, we obtain accurate values of the c -axis superfluid density, $\lambda^2(0)/\lambda^2(T)$, and the optical conductivity at the resonance frequency, $\sigma_1(\omega_J)$, as a function of temperature.

In Fig. 3 we present the temperature dependance of the c -axis superfluid density, $\lambda^2(0)/\lambda^2(T)$ and the c -axis superfluid density of LSCO of Ref. [9]. Fitting the c -axis superfluid density to a powerlaw $\lambda^2(0)/\lambda^2(T) = 1 - (T/T_0)^\eta$ for temperatures below $0.5T_c$ we obtain an exponent $\eta = 2.1$ for Tl2201, $\eta = 2.4$ for Tl2212. Hence our results show that

there is also no linear temperature dependence for the c -axis superfluid density in Tl2201, and Tl2212, as has been observed in several other high T_c materials. [11–13] The behavior in both Tl-based compounds is close to quadratic. In Fig. 3b we present the c -axis optical conductivity versus temperature for Tl2201, Tl2212 and LSCO. In all compounds σ_c exhibits a smooth drop below T_c . The drop in $\sigma_c(T)$ has also been observed in YBCO and Bi2212, and is very different from the temperature dependence of the ab -plane conductivity, where $\sigma_{ab}(T)$ shows a large peak below T_c , attributed to a rapid increase in the quasiparticle lifetime. The absence of a subsequent rise of σ_c at lower temperature indicates that effectively we observe no enhancement of the quasiparticle life time for this transport direction.

Recently Xiang and Wheatley [21] calculated the c -axis response assuming d-wave pairing, and assuming a model for the c -axis transport where momentum parallel to the planes, $k_{\parallel}$, is conserved. Based on LDA band theoretical results [22], they argued that for HTSC's with a simple (non-body centered) tetragonal structure, $t_{\perp} \propto (\cos(k_x a) - \cos(k_y a))^2$, leading to an exponent $\eta = 5$ at low temperature. Allowing some scrambling of $k_{\parallel}$ due to impurity scattering during the interplane hopping, reduces this to $\eta = 2$ at very low temperatures, crossing over to the T^5 above a temperature which depends on the impurity scattering rate.

Within the same line of thinking, Ioffe and Millis [1] recently proposed that the scattering lifetime has a strong dependence on $k_{\parallel}$ along the two-dimensional Fermi-surface, namely

$$\Gamma(k_{\parallel}) = \frac{\Gamma_0}{4} \sin^2(2\Theta) + \frac{1}{\tau} \quad (3)$$

where Θ is the angle of $k_{\parallel}$ relative to the diagonal ('nodal') direction. For the in-plane response this leads to an expression for the optical conductivity which fits the in-plane experimental spectra rather well, and has the prototypical property of the optimally doped cuprates that the effective scattering rate $1/\tau^* \equiv \omega \text{Re}\sigma / \text{Im}\sigma$ has a linear frequency dependence if Γ_0 is assumed to be temperature independent, while $1/\tau \propto T^2$.

For the c -direction, we must take into account, that $t_{\perp} \propto (\cos(k_x a) - \cos(k_y a))^2$, as has been done by Xiang and Wheatley [21]. The c -axis transport arises in this picture from regions at the Fermi-surface well removed from the nodes of the gap. Due to the strong suppression of $t_{\perp}^2$ along the nodal directions, $\sigma_c(\omega)$ probes only regions away from the nodes, closer to the regions of maximum gap value. In those regions of k -space $\hbar\Gamma(k_{\parallel})$ is large, of order 1 eV. This places the c -axis optical conductivity well inside the dirty limit [23], and it provides a simple microscopic argument why an analysis of the c -axis optical conductivity in the superconducting state, using the Mattis-Bardeen expressions for s -wave superconductors compares so well to the experimental data [9].

The question of how to understand the large difference in scattering properties and gap observed along two different optical axes, has thus been shifted to a strong dependence of the scattering rate on the position along the Fermi-surface (which is a *phenomenological* assumption) and a strong dependence of the hopping parameter on $k_{\parallel}$ (which is a straightforward result of band-theory). The 'confinement' in the sense of an anomalous renormalization of the transport properties due to many-body effects, is in this picture associated with the anti-nodal regions in k -space. Near the nodal-regions the confinement is dominated by a straight-forward single-particle effect on $t_{\perp}(k_{\parallel})$, which follows directly from band-theory. However, the anti-correlation between these two kinds of confinement seems hardly a coincidence, and certainly deserves further attention. This leaves open the question of the microscopic implications of this phenomenological model. The correspondence between $\Delta(k_{\parallel})$ and $t_{\perp}$ has been previously attributed to the interlayer tunneling mechanism [3]. Likewise the correspondence between $\Delta(k_{\parallel})$ and $\Gamma(k_{\parallel})$ may contain important clues regarding the pairing mechanism leading to superconductivity.

In conclusion, we have observed the c -axis Josephson plasma resonance in Tl2201 and Tl2201. The values of the resonant frequencies in the two compounds are quite close, which indicates that the weakest link is the inter-cell link. In a magnetic field of 0.35 T the resonance is completely pushed out of our spectral window, which is the expected behavior for the Josephson collective excitation. From our data, we were able to extract the c -axis superfluid density, and conductivity $\sigma_c(T)$. The temperature dependence of both quantities indicate two-dimensional confinement of the charge carriers.

*Also P. N. Lebedev Physical Institute, Moscow.

[1] L. B. Ioffe, and A. J. Millis, Phys. Rev. B **58**, 11631 (1998).

[2] P. W. Anderson, *The Theory of Superconductivity in the High- T_c Cuprates*, (Princeton University Press, Princeton, NJ, 1997).

[3] S. Chakravarty and P. W. Anderson, Phys. Rev. Lett. **72**, 3859 (1994).

- [4] P. W. Anderson, Science **268**, 1154, (1995); D. van der Marel et al, Proceedings of the 10th Anniversary HTS Workshop on Physics, Materials and Applications p 357 (World Scientific, Rivers Edge, NJ, 1996); A. J. Leggett, Science **274**, 587, (1996).
- [5] J. Schützmann, *et al.*, Phys. Rev. B **55**, 11118 (1997).
- [6] K. A. Moler *et al.*, Science **279**, 1193 (1998).
- [7] A. A. Tsvetkov *et al.*, Nature, **395**, 360 (1998).
- [8] K. Tamasaku, Y. Nakamura, and S. Uchida, Phys. Rev. Lett. **69**, 1455 (1992). The drop of the quasi-particle scattering rate reported in Fig. 1 of this article was in fact the plasma-resonance line-width (S. Uchida, private communication). As discussed in the text of the present article this represents $\sigma_c(\omega_J)$ at the resonance-frequency.
- [9] J. H. Kim *et al.*, Physica C **247**, 597, (1995).
- [10] H. Kitano *et al.*, Phys. Rev. B. **57**, 10946 (1998).
- [11] A. Hosseini *et al.*, Phys. Rev. Lett. **81**, 1298, (1998).
- [12] T. Xiang *et al.*, International J. of Modern Phys. B **12**, 1007, (1998).
- [13] T. Jacobs *et al.*, Phys. Rev. Lett. **75**, 4516, (1995).
- [14] C. A. Wang *et al.*, Physica C **262**, 98 (1996).
- [15] B. A. Willemsen *et al.*, Phys. Rev. B. **58**, 6650 (1998).
- [16] M. M. Eddy, U.S. Patent Nos. 5,476,836 (1995) and 5,508,255 (1996)
- [17] A. A. Tsvetkov *et al.*, Phys. Rev. B, in press.
- [18] D. van der Marel and A. A. Tsvetkov, Czech. J. of Phys. **46** 3165 (1996).
- [19] C.C. Homes *et al.*, Phys. Rev. Lett. **71** 1645 (1993).
- [20] D. N. Basov *et al.*, Science **283**, 49 (1999).
- [21] T. Xiang and J. M. Wheatley, Phys. Rev. Lett. **77**, 4632 (1996).
- [22] O.K. Anderson *et al.*, Phys. Rev. B **49**, 4145 (1995).
- [23] D. van der Marel, cond-mat 9904254 (1999).

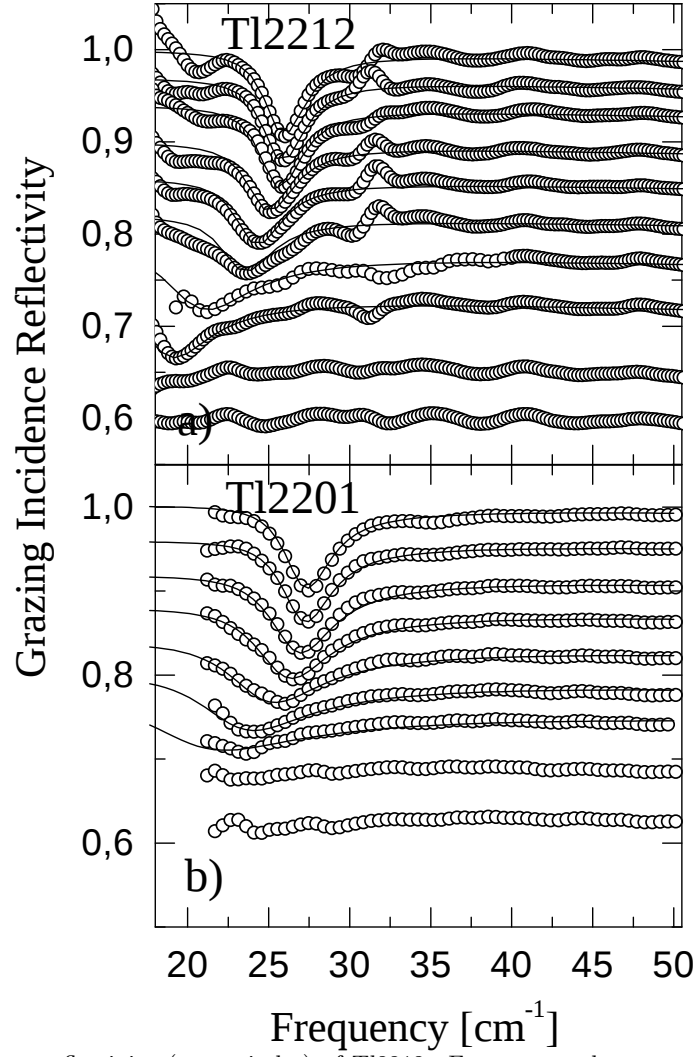


FIG. 1. a) Grazing incidence reflectivity (open circles) of Tl2212. From top to bottom: 4K, 10K, 20K, 30K, 40K, 50K, 60K, 70K, 80K and 110K. The curves have been offset for clarity. The solid curves are fits to the data. b) Grazing incidence reflectivity (open circles) of Tl2201, at 4K, 10K, 20K, 30K, 40K, 50K, 60K, 75K, and 90K. The solid curves are fits to the data.

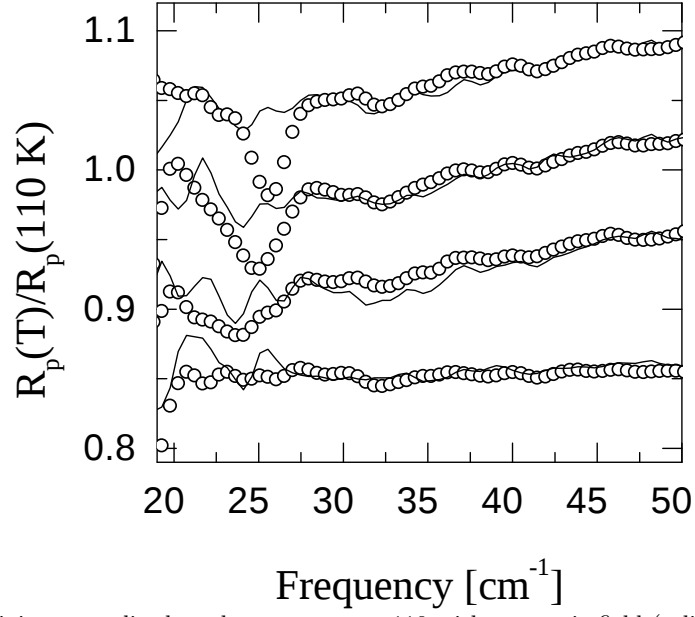


FIG. 2. P-polarized reflectivity normalized to the spectrum at 110 with magnetic field (solid curve) and without magnetic field (open circles). From top to bottom: 4K, 30K, 60K, 90K.

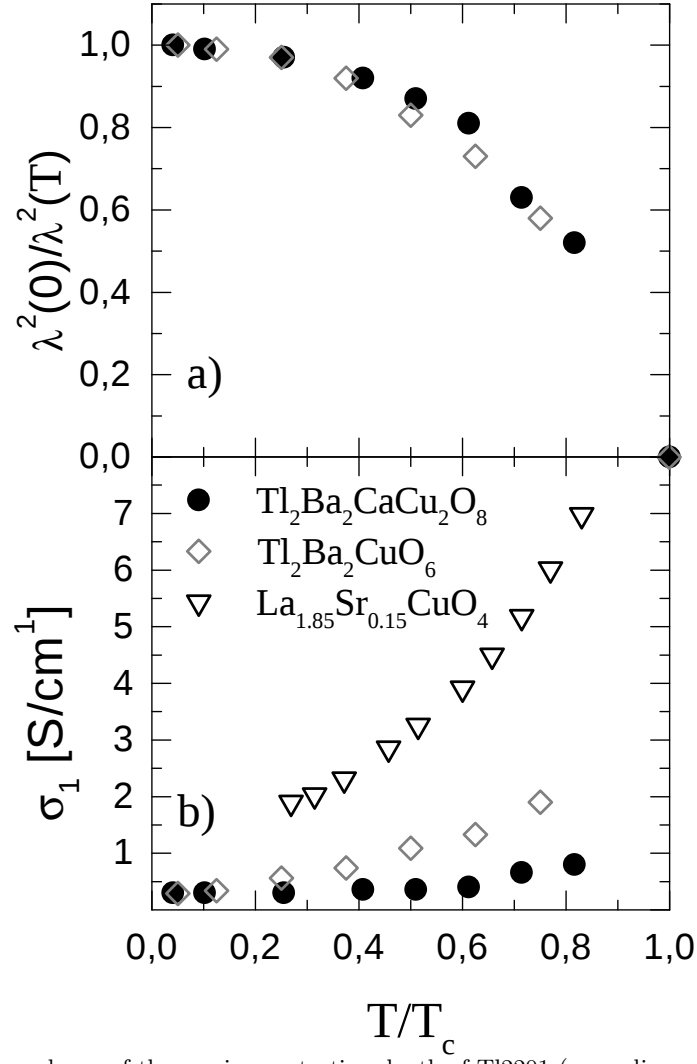


FIG. 3. a) Temperature dependence of the c -axis penetration depth of Tl2201 (open diamonds), and Tl2212 (solid circles). b) Temperature dependence of the c -axis optical conductivity of Tl2201, Tl2212, and LSCO